

# HIGH SPEED STEELS

## Available Product Variants

Long Products\*

Plates

\* ) Presented data refer exclusively to long products. Please observe the detailed explanations at the end of the data sheet (pdf).

## Product Description

### BÖHLER S390 MICROCLEAN – "The decathlete"

This grade is our PM steel with many positive usage properties. For twist drills, taps, mills, broaches, or cold-work applications, BÖHLER S390 MICROCLEAN is always a high performer.

## Process Melting

Powder metallurgy

## Properties

- > Toughness & Ductility : high
- > Wear Resistance : high
- > Compressive strength : very high
- > Edge Stability : very high
- > Grindability : high
- > Hot Hardness (red hardness) : very high

## Applications

- > Automotive Racing
- > End Mills
- > Powder Pressing
- > Special Cutting Tools
- > Pill punching dies
- > Broaches and Reamers
- > Fine Blanking, Stamping, Blanking
- > Rolling
- > Twist Drills and Taps
- > Cold Forming / Coining
- > Gear Cutting, Shaving and Shaping Tools
- > Shearing / Machine Knives
- > Wear parts

## Chemical composition (wt. %)

C	Cr	Mo	V	W	Co
1.64	4.80	2.00	4.80	10.40	8.00

### Material characteristics

	Compressive strength	Grindability	Red hardness	Toughness	Wear resistance	Edge Stability
<b>BÖHLER S390</b> MICROCLEAN®	★★★★	★★★	★★★★	★★★★	★★★★	★★★★
<b>BÖHLER S290</b> MICROCLEAN®	★★★★★	★	★★★★	★★	★★★★★	★★★★
<b>BÖHLER S393</b> MICROCLEAN®	★★★★	★★★	★★★★	★★★★	★★★★	★★★★
<b>BÖHLER S590</b> MICROCLEAN®	★★★★	★★★	★★★★	★★★	★★★	★★★
<b>BÖHLER S690</b> MICROCLEAN®	★★★	★★★	★★	★★★★★	★★★	★★
<b>BÖHLER S790</b> MICROCLEAN®	★★★	★★★	★★	★★★★	★★	★★★
<b>BÖHLER S792</b> MICROCLEAN®	★★★	★★★	★★	★★★★	★★	★★★
<b>BÖHLER S793</b> MICROCLEAN®	★★★	★★★	★★★★	★★★	★★★	★★★

### Delivery condition

#### Annealed

Hardness (HB)	max. 320   drawn execution max. 320 HB
Tensile Strength (N/mm <sup>2</sup>   ksi)	max. 1,080   157

#### Hardened and Tempered

Hardness (HRC)	64 to 68
----------------	----------

### Heat treatment

#### Annealing

Temperature	870 to 900 °C   1,598 to 1,652 °F	4 h, controlled slow cooling in furnace ( 10 to 20°C/h / (50 to 68°F/h) to 740°C/2h (1364°F/2 h) cooling in furnace,
-------------	-----------------------------------	--

#### Stress relieving

Temperature	600 to 650 °C   1,112 to 1,202 °F	Slow cooling in furnace.    To relieve stresses set up by extensive machining or in tools of intricate shape.    After through heating, hold in neutral atmosphere for 1 to 2 hours.
-------------	-----------------------------------	--

#### Hardening and Tempering


Temperature	1,100 to 1,200 °C   2,012 to 2,192 °F	Salt bath, vacuum    Preheating: 1st stage ~ 500 °C (930 °F), 2nd stage ~ 850 °C (1560 °F), 3rd stage ~1050 °C (1920 °F)    Austenitising: 1100 - 1200 °C (2010 °F - 2190 °F), holding time after complete heating 80 seconds, maximum 150 seconds, to avoid material damage due to overheating.    Quenching: oil, warm bath (500 - 550 °C (930 °F - 1020 °F)), gas
Temperature	550 to 570 °C   1,022 to 1,058 °F	Slow heating to tempering temperature immediately after austenitising.    Holding time in the furnace 1 hour per 20 mm material thickness (at least 1 hour)    Slow cooling to room temperature between each tempering step    3 tempering cycles recommended    Hardness see tempering chart

**Continuous cooling CCT curves**

Austenitising temperature: 1230°C  
Haltedauer: 180 Sekunden

Austenitising temperature: 1230°C (2246°F)  
Holding time: 180 seconds

Austenitising temperature: 1230°C (2246°F)  
Holding time: 180 seconds

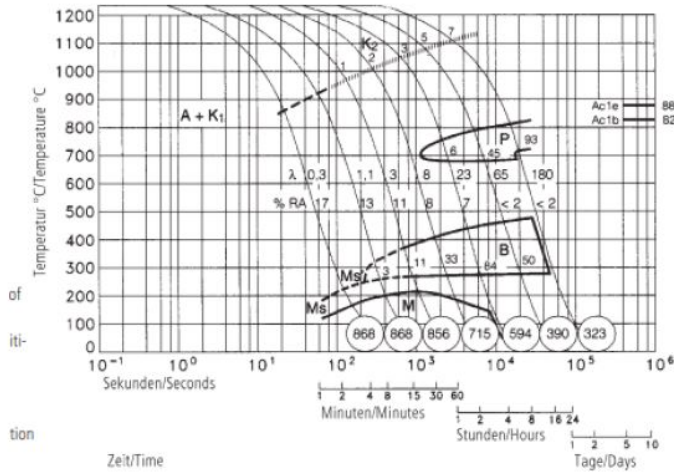


A...Austenite  
B...Bainite  
K...Carbide  
P...Pearlite  
M...Martensite  
RA...Retained Austenite

**Quantitative phase diagram**

Austenitising temperature: 1230°C  
Haltedauer: 180 Sekunden


Austenitising temperature: 1230°C (2246°F)  
Holding time: 180 seconds

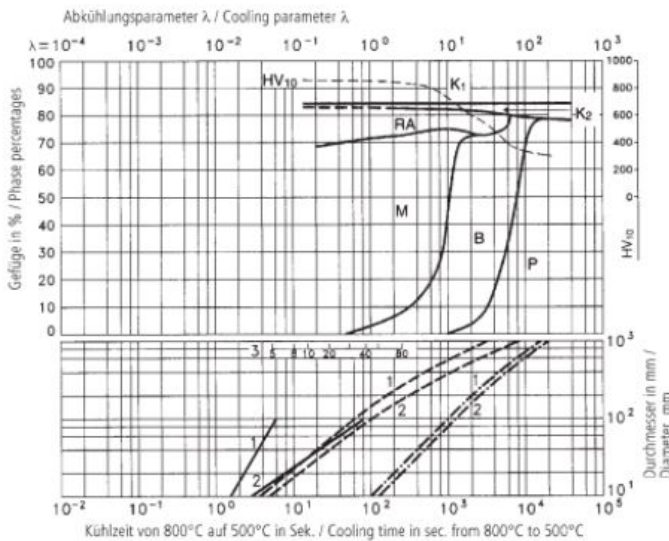

A...Austenite  
B...Bainite  
K...Carbide  
P...Pearlite  
M...Martensite  
RA...Retained Austenite

1...Edge or Face  
2...Core  
3...Jominy test: distance from quenched end

### Tempering Chart

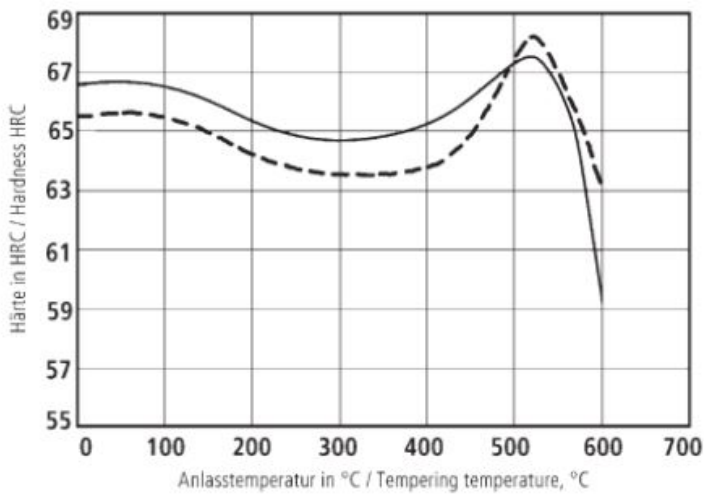

Holdingtime 3x2 hours

Specimensize: square 25mm

Austenitising in saltbath

Hardeningtemperature:

—— 1150°C (2102°F)

----- 1210°C (2210°F)

### Physical Properties

Temperature (°C   °F)	20   68
Density (kg/dm <sup>3</sup>   lb/in <sup>3</sup> )	8.1   0.29
Thermal conductivity (W/(m.K)   BTU/ft h °F)	17   9.82
Specific heat (kJ/kg K   BTU/lb °F)	0.42   0.1003
Spec. electrical resistance (Ohm.mm <sup>2</sup> /m   10 <sup>-4</sup> Ohm.inch <sup>2</sup> /ft)	0.61   2.88
Modulus of elasticity (10 <sup>3</sup> N/mm <sup>2</sup>   10 <sup>3</sup> ksi)	231   33.5

**Thermal Expansions between 20°C | 68°F and ...**

Temperature (°C   °F)	100   212	200   392	300   572	400   752	500   932	600   1,112	700   1,292
Thermal expansion (10 <sup>-6</sup> m/(m.K)   10 <sup>-6</sup> inch/inch.°F)	10   5.6	10.5   5.8	10.8   6	11.2   6.2	11.3   6.3	11.4   6.3	11.6   6.4

**Long Products:** For additional specifications and technical requirements, please contact our regional voestalpine BÖHLER sales companies.

**Sheet & Plates:** Product Variant may differ in terms of melting process, technical data, delivery, and surface condition as well as available product dimensions. Please contact voestalpine BÖHLER Bleche GmbH & Co KG.

*The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.*